



Release Notification Date: 01/16/2023

SPM 70-33-08 REPLICATION TO IDENTIFY EVIDENCE OF FOREIGN MATERIAL AFTER BLENDING

**DISCLAIMER**

The Incremental Changes published by GE Aviation are considered Instructions for Continued Airworthiness. These Incremental Changes, along with the current Manual revision and published Temporary Revisions, constitute the latest Instructions for Continued Airworthiness.

**GE Designated: -CONFIDENTIAL-**

The information contained in this document is GE proprietary information and is disclosed in confidence. It is the property of GE and shall not be used, disclosed to others or reproduced without the express written consent of GE, including, but without limitation, it is not to be used in the creation, manufacture, development, or derivation of any repairs, modifications, spare parts, designs, or configuration changes or to obtain FAA or any other government or regulatory approval to do so. If consent is given for reproduction in whole or in part, this notice and the notice set forth on each page of this document shall appear in any such reproduction in whole or part.

This technical data is considered subject to the Export Administration Regulations (EAR) pursuant to 15 CFR Parts 730-774. Transfer of this data by any means to a Non-U.S. Person, whether in the United States or abroad, without the proper U.S. Government authorization (e.g., License, exemption, NLR, etc.), is strictly prohibited.

Copyright (2023) General Electric Company, U.S.A.

HIGHLIGHTS

<u>HIGHLIGHT REFERENCE</u>	<u>DESCRIPTION OF CHANGE</u>
sk70-33-08-220-132	Technical Change: Changed instruction to perform an evaluation of the replica(s).
sk70-33-08-120-034	Technical Change: Added figures for the instruction to polish the etched area(s) to remove the effects of etching.

TASK 70-33-08-220-000

1. General.

- A. This procedure gives instructions for the preparation, replication, and evaluation of surfaces to make sure there is no evidence of foreign material after blending for R88DT, R104, R65, and Inco 718 materials.
- B. This procedure requires suitably trained personnel. Verification shall be determined by replicating and correctly evaluating the results against photo standards.
- C. This procedure is required to be applied at each location of localized pitting or deposited material.

2. Equipment.

- A. Tools and Equipment
  - (1) Special Tools

**Description**

Microscope with measuring capability at 100X to 500X  
Glass slide

- B. Standard Tools and Equipment

**Description**

Scissors  
High precision tweezers\*  
Nonabrasive cloth

**NOTE:** \*High precision tweezers can be obtained from TED PELLA, INC. Product code #5622 (SS 110mm).

3. Materials.

Consumable Product	No.
Solvent, General (isopropyl alcohol)	C04-035
Solvent, General (acetone)	C04-003
Thick Replicating Tape, 125m	C10-254
Abrasive Paper (6 micron diamond paste or finer abrasive)	C10-255
Hydrochloric Acid	C04-071
Solvent, General (94-96% assay ethanol)	C04-228
Cupric Chloride Dihydrate	C04-302
Alcohol, Methyl	C04-180

4. Procedure.

Subtask 70-33-08-160-015

**WARNING:** REFER TO THE PRODUCT LABEL AND THE MANUFACTURER'S (MATERIAL) SAFETY DATA SHEET (SDS) FOR INSTRUCTIONS ON THE HAZARDS, STORAGE, SAFE HANDLING AND PROPER USE OF CONSUMABLE PRODUCTS.

- A. Clean with isopropyl alcohol C04-035 or acetone C04-003 to prepare the area for polishing. Make sure that the surface is free of any contamination (for example grit and oil).

Subtask 70-33-08-120-033

- B. Remove all machining marks by sanding, using successively finer abrasives. The final polish shall be performed with abrasive paper C10-255.

**NOTE:** For best replica results, alternate the polishing direction as finer abrasive papers are applied to the area. This will help avoid evidence scratches on the replica.

Subtask 70-33-08-110-537

- C. Clean the polished areas with isopropyl alcohol C04-035 or acetone C04-003 and a suitable nonabrasive cloth. Make sure that the surface is free of any contamination (for example grit and oil).
- D. Prepare the Kallings Etchant Solution with the following composition. Larger or smaller quantities may be mixed, as desired, as long as proportions are equal to those given.

**Kallings Etchant Ingredients - Table 1**

C04-302	Cupric Chloride Dihydrate	2 gr
C04-071	Hydrochloric Acid	40 mL
C04-228 or C04-180	Ethanol or Methyl Alcohol	40-80 mL

**NOTE:** Shelf life of kallings etchant is 2 weeks.

Subtask 70-33-08-110-538

**CAUTION:** MAKE SURE TO DO A CHECK OF THE ENVIRONMENT REGULATIONS BEFORE DISCARDING SOLUTIONS.

- E. Etch the polished area(s) in preparation for the surface microstructure examination refer to TASK 70-24-01-110-034, Swab Etching Procedure for details on the application process requirements (localized and careful application).

- (1) Etch the polished area(s) for 60-90 seconds. Pay attention to any dark discoloration in the etched surface (this is a signal that the etchant has been applied too long or there is still evidence of foreign material).

**NOTE:** If you need to repeat the etching process, do not pass the total time of 180 seconds.

**WARNING:** THE ACTIVE INGREDIENTS OF ETCHANTS ARE TOXIC AND CORROSIVE. USE IN A WELL VENTILATED AREA, WEAR PROTECTIVE CLOTHING, GLOVES AND FACE SHIELD. AVOID PROLONGED BREATHING OF VAPORS AND CONTACT WITH THE SKIN. IF ETCHING SOLUTION GETS INTO EYES, FLUSH THOROUGHLY WITH COOL WATER UNDER EYELIDS, AND OBTAIN MEDICAL ATTENTION AT ONCE.

**WARNING:** REFER TO THE PRODUCT LABEL AND THE MANUFACTURER'S (MATERIAL) SAFETY DATA SHEET (SDS) FOR INSTRUCTIONS ON THE HAZARDS, STORAGE, SAFE HANDLING AND PROPER USE OF CONSUMABLE PRODUCTS.

**CAUTION:** DO NOT POUR WORKING SOLUTION BACK INTO STOCK CONTAINER. DISPOSE OF THE USED WORKING SOLUTION IN ACCORDANCE WITH LOCAL ENVIRONMENTAL, HEALTH, AND SAFETY REGULATIONS.

- F. Wash off the polished area(s) with isopropyl alcohol C04-035 or acetone C04-003.

**NOTE:** Make sure that all evidence of the etchant solution is all removed.

- G. Perform a microstructure replication of all of the etched area(s), as follows:

- (1) Cut a piece of replicating tape larger than the area to be replicated.
- (2) Wet the surface of the part to be replicated, or one side of the replicating tape with acetone C04-003 or other approved solvent.
- (3) Place replicating tape on the area to be replicated and allow to dry. The typical drying time for a 0.005 inch (0.13 mm) tape wet with acetone is about 10 minutes.
- (4) Use a high precision tweezers lift one corner of the replicating tape and remove tape.
- (5) Place the replica tape on a clean glass slide, with the replicated face not in contact with the glass.
- (6) Put a mark on the replica slide, the location of the area examined, and the serial number of the part.

Subtask 70-33-08-220-132

- H. Perform an evaluation of the replica(s), as follows:

- (1) Use a microscope and examine replica(s) at 100X, at 200X or at 500X magnification. When applicable, higher magnification may be used.
- (2) Evaluate the replica(s) for conformance. Refer to Figure 1 for photo standard examples of acceptable replicas.
- (3) Refer to Figure 2 for typical replica defects that are not indicative of foreign material. If these defects are excessive (i.e., they cover more than 1/4 of the replica area and

obscure the normal grain boundary structure of the material) the replica must be made again, or contact GE Engineering for further assessment.

**NOTE:** An acceptable replica will show the normal grain boundary structure of the material.

**NOTE:** This step should only be performed by trained personnel in the field of material grain boundary microscopy.

(4) If there is no evidence of any foreign material present, the assessment is acceptable.

**NOTE:** No grain boundaries or large areas of no grain boundaries shows foreign material is present.


**NOTE:** Any suspect evidence of foreign material must be sent to GE Engineering for further assessment. Please include the details that follow: part number and serial number, customer/operator, time since new, cycles since new, time since overhaul, and cycles since overhaul. This information can be submitted as a Service Request (SR) via myGEAviation.com. Alternatively, send photos of replica with a scale bar included for the magnification used, to Support at Aviation.Fleetsupport@ge.com.

Subtask 70-33-08-120-034

I. Polish the etched area(s) to remove the effects of etching, as follows:

(1) Polish with abrasive cloth C10-010. Make sure a surface finish equal to, or better than the adjacent area is achieved.

\* \* \* FOR ALL

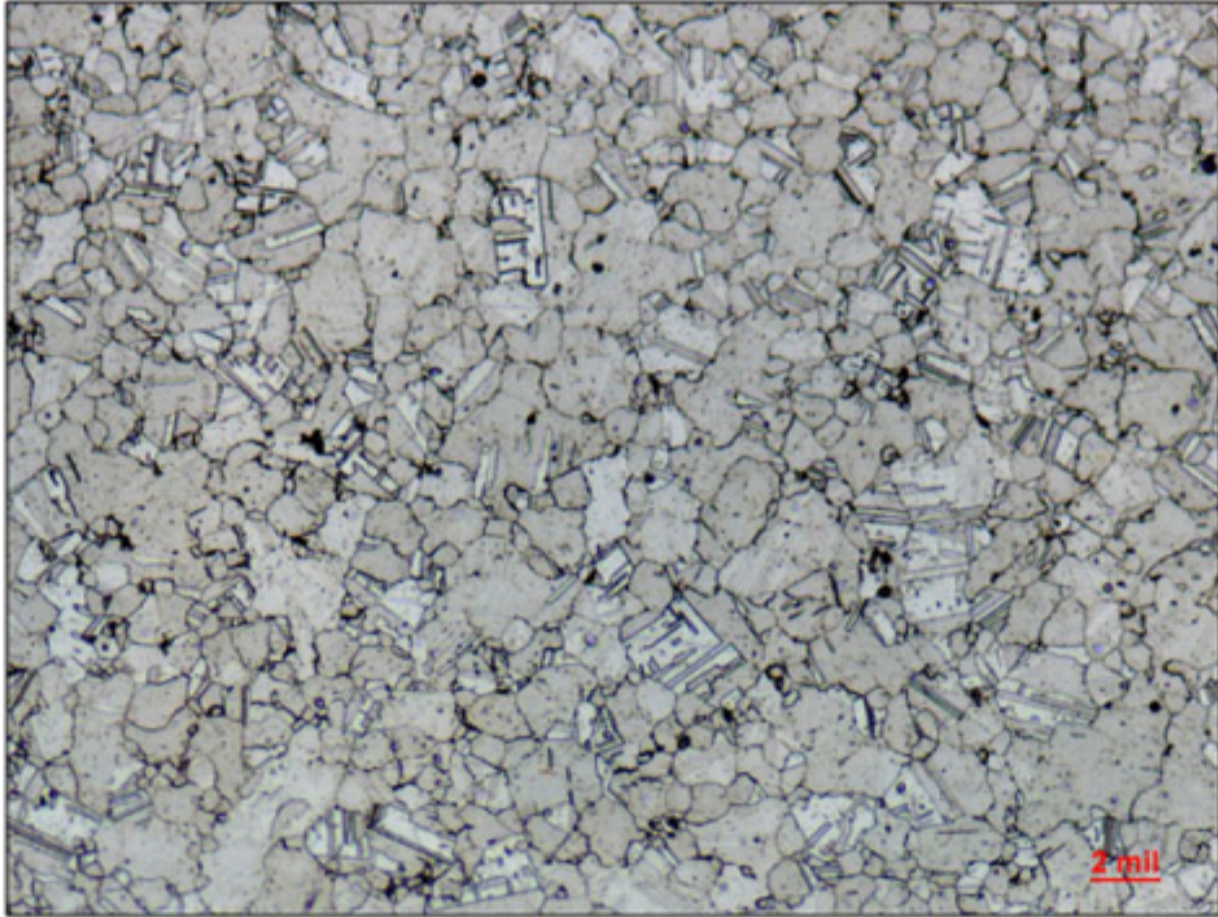


**NORMAL RENE'88DT  
100X MAGNIFICATION**

6002881-00

Figure 1 (Sheet 1) Normal Grain Structure from Replication.

\* \* \* FOR ALL



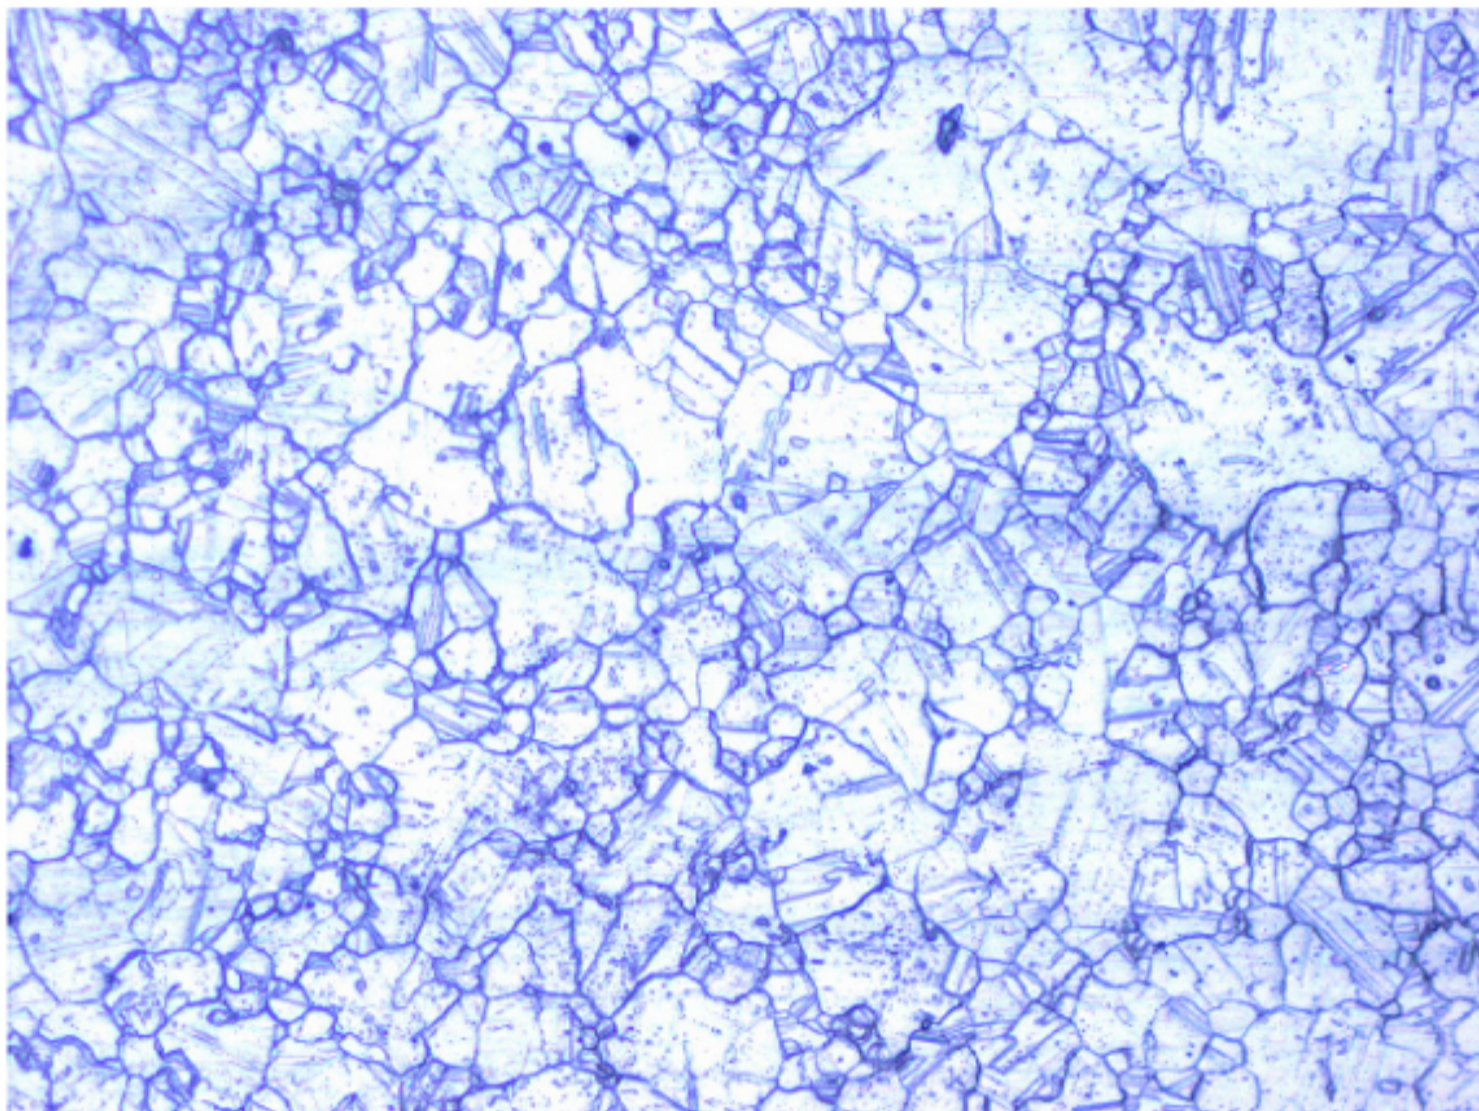

**NORMAL RENE 88DT  
200X**

6038597-00

Figure 1 (Sheet 2) Normal Grain Structure from Replication

\* \* \* FOR ALL






**NORMAL RENE 65  
100X MAGNIFICATION**

6002880-00

Figure 1 (Sheet 3) Normal Grain Structure from Replication

\* \* \* FOR ALL

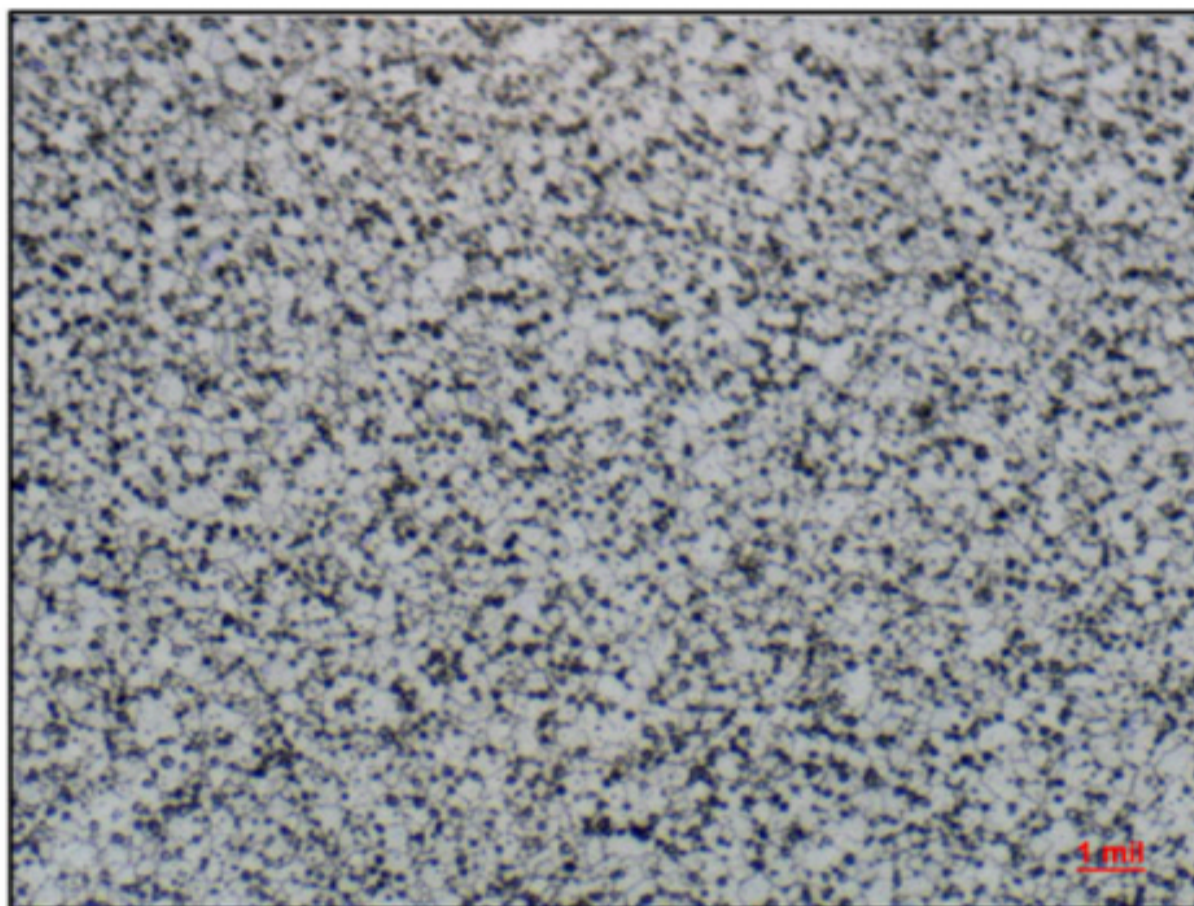


**NORMAL RENE 65  
200X MAGNIFICATION**

6002822-00

Figure 1 (Sheet 4) Normal Grain Structure from Replication

\* \* \* FOR ALL



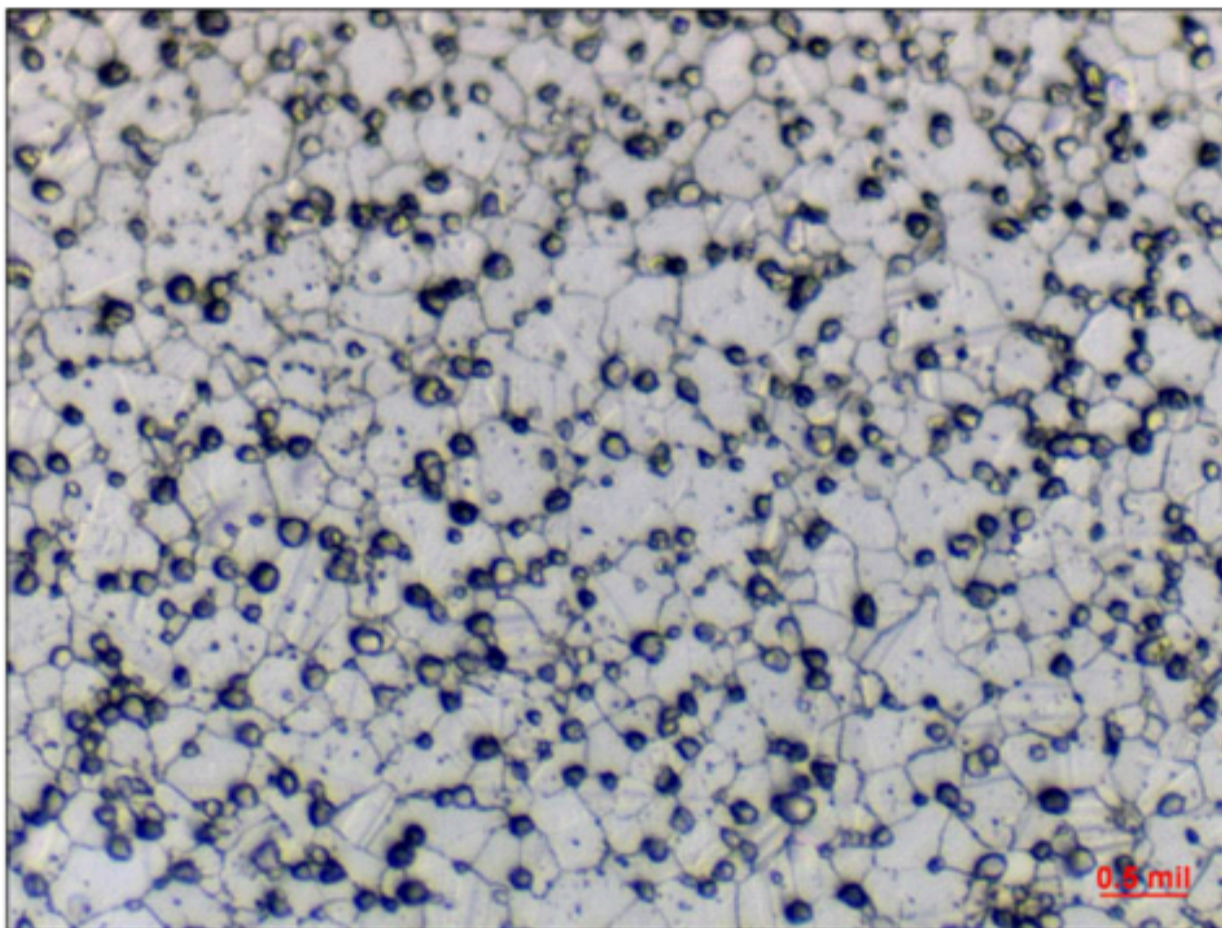


**NORMAL RENE 65  
500X MAGNIFICATION**

6002821-00

Figure 1 (Sheet 5) Normal Grain Structure from Replication

\* \* \* FOR ALL



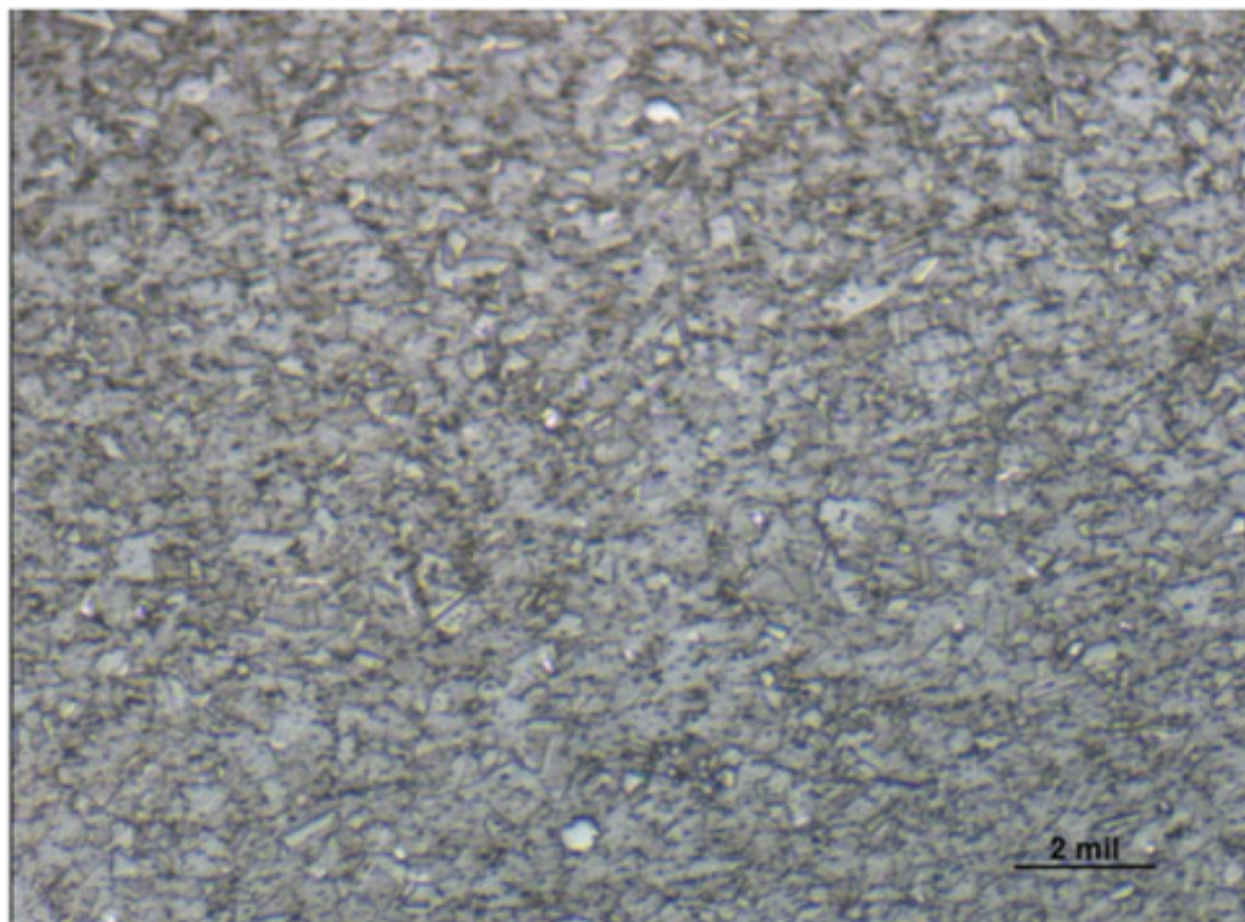


**NORMAL DA718  
200X MAGNIFICATION**

6002820-00

Figure 1 (Sheet 6) Normal Grain Structure from Replication

\* \* \* FOR ALL

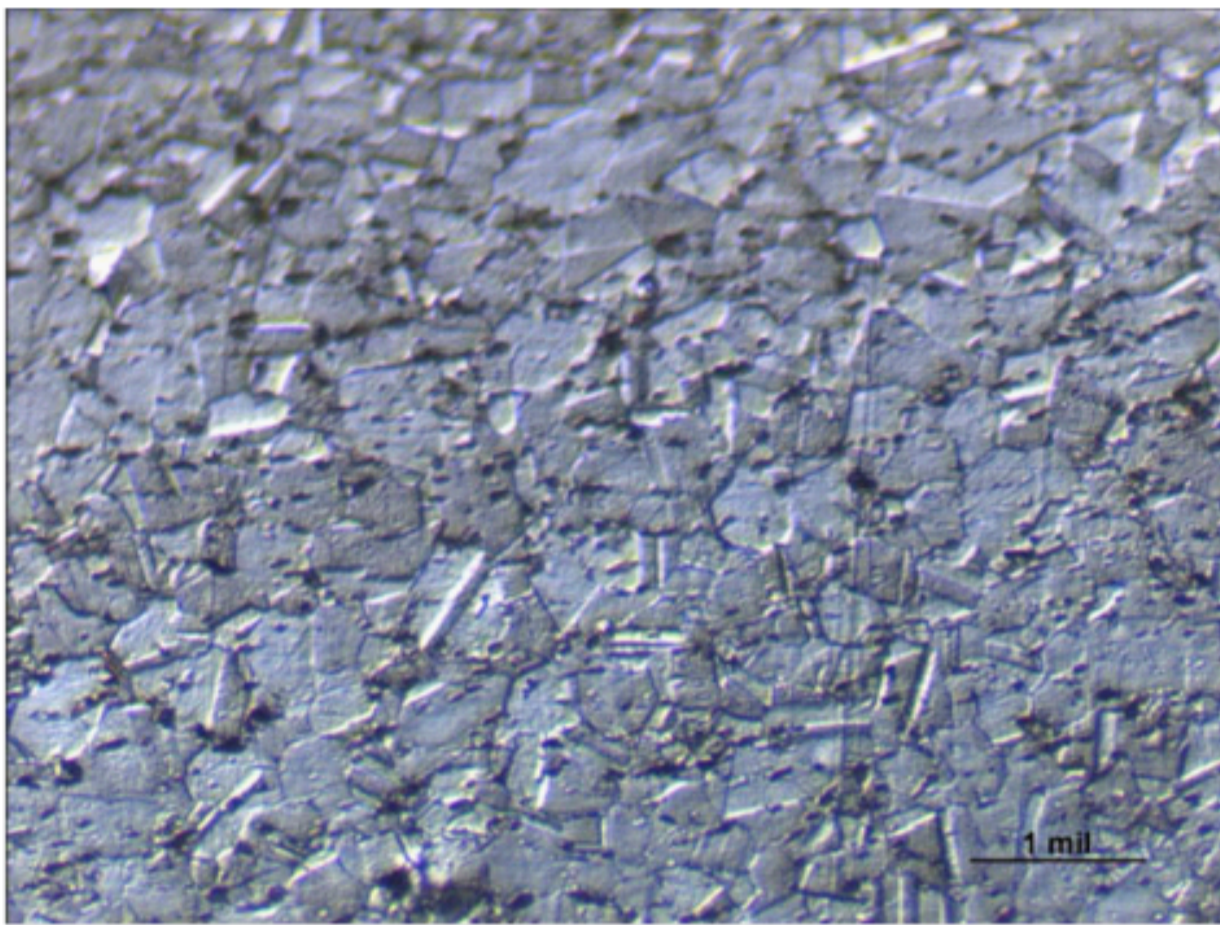

**NORMAL DA718  
500X MAGNIFICATION**

6002819-00

Figure 1 (Sheet 7) Normal Grain Structure from Replication

\* \* \* FOR ALL






**NORMAL RENE 104  
100X MAGNIFICATION**

6002818-00

Figure 1 (Sheet 8) Normal Grain Structure from Replication

\* \* \* FOR ALL

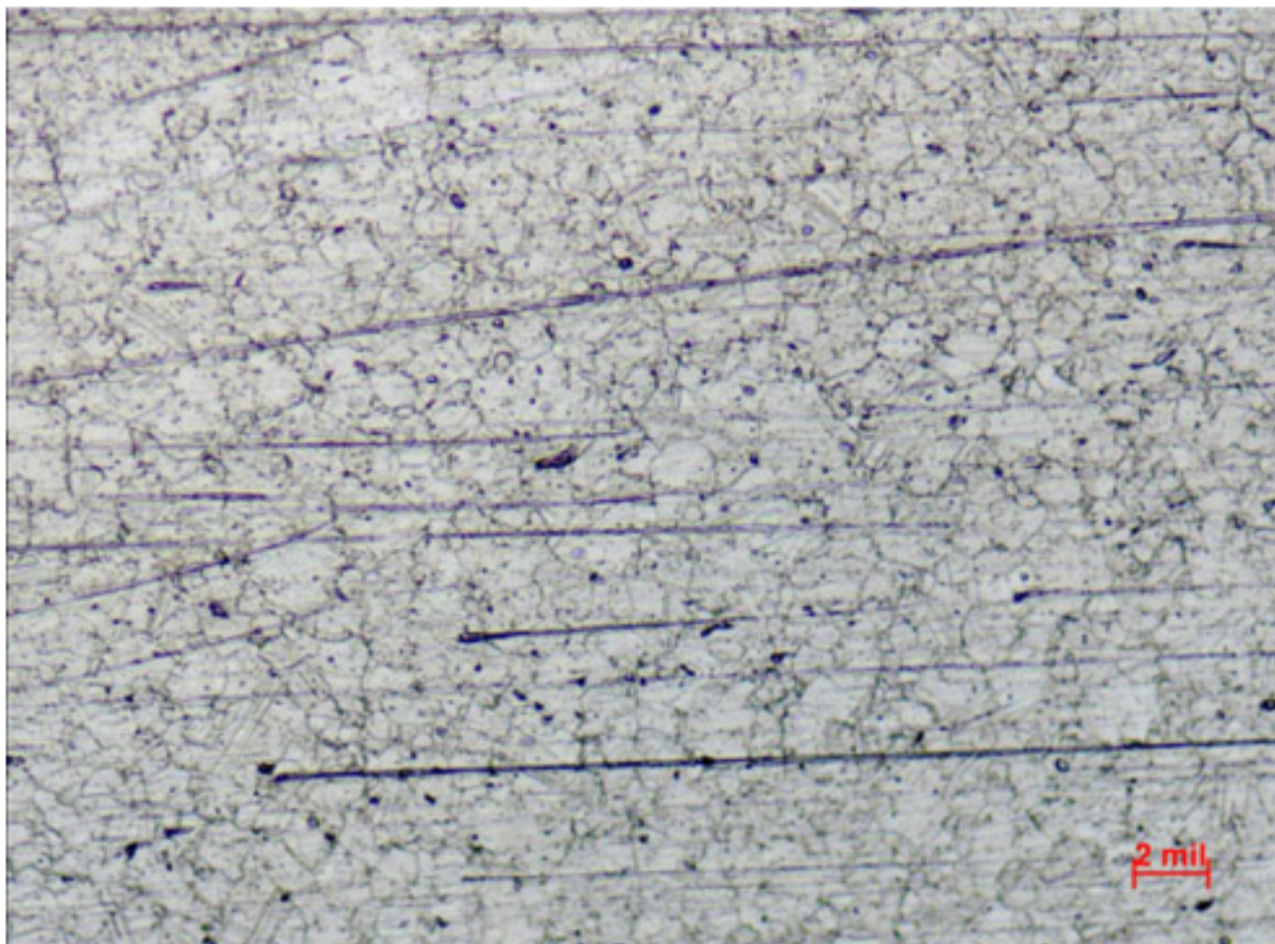


**SCRATCHES**

6002817-00

Figure 2 (Sheet 1) Grain Structure from Replication Rene'88DT with Scratches.

\* \* \* FOR ALL



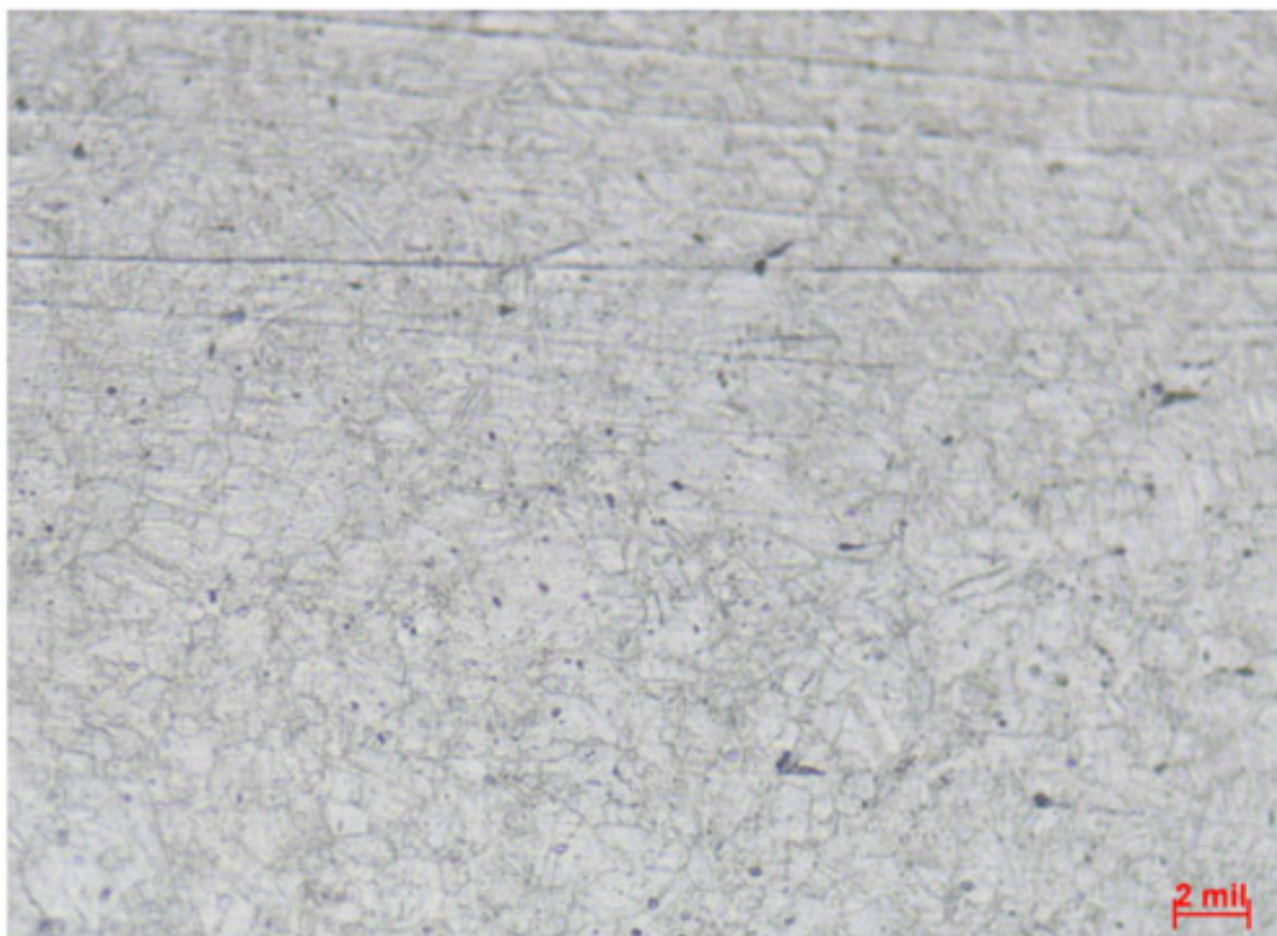


**UNDER ETCHED**

6002816-00

Figure 2 (Sheet 2) Grain Structure from Replication Rene'88DT Under Etched.

\* \* \* FOR ALL

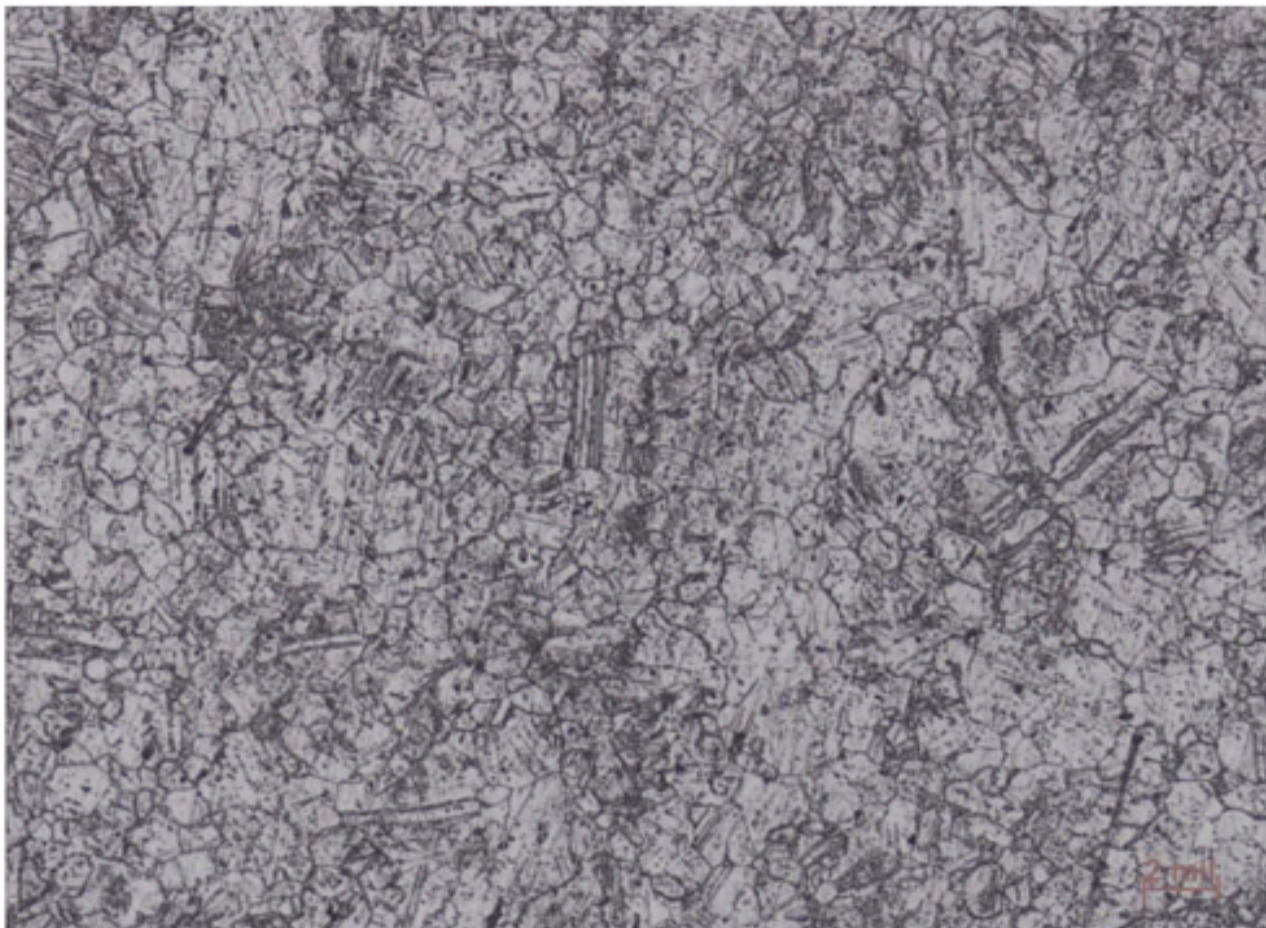


**OVER ETCHED**

6002814-00

Figure 2 (Sheet 3) Grain Structure from Replication Rene'88DT Over Etched.

\* \* \* FOR ALL



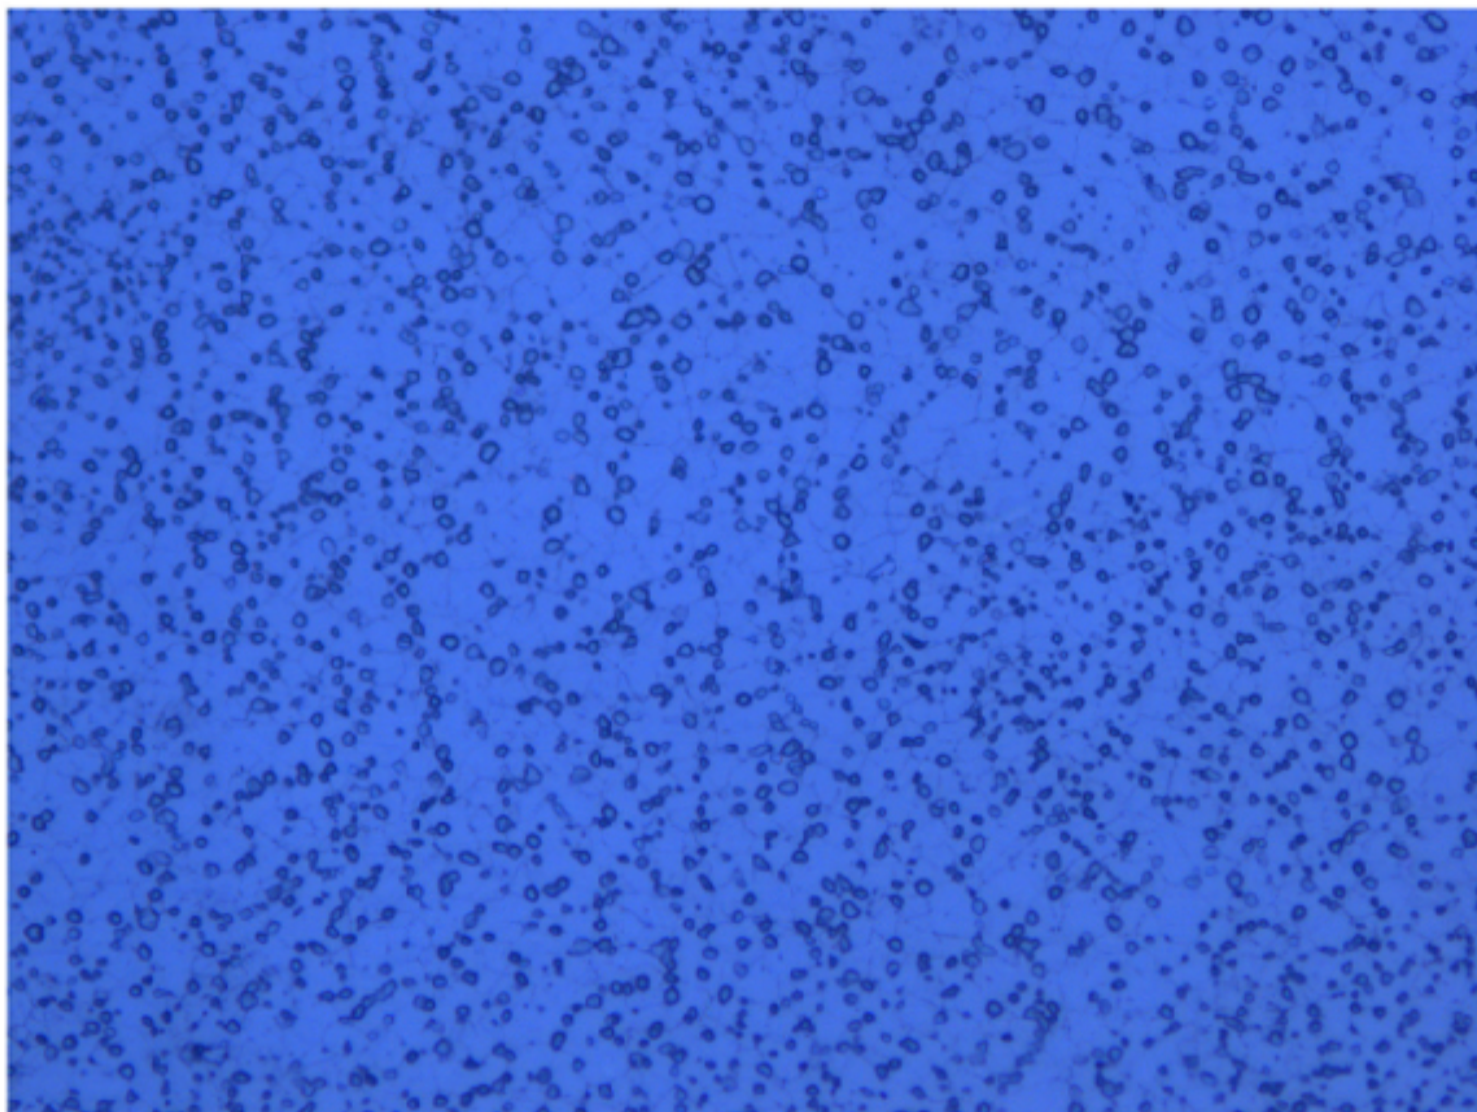


UNDERETCHED  
RENE 65

6038598-00

Figure 2 (Sheet 4) Grain Structure from Replication Rene'65 Under Etched

\* \* \* FOR ALL



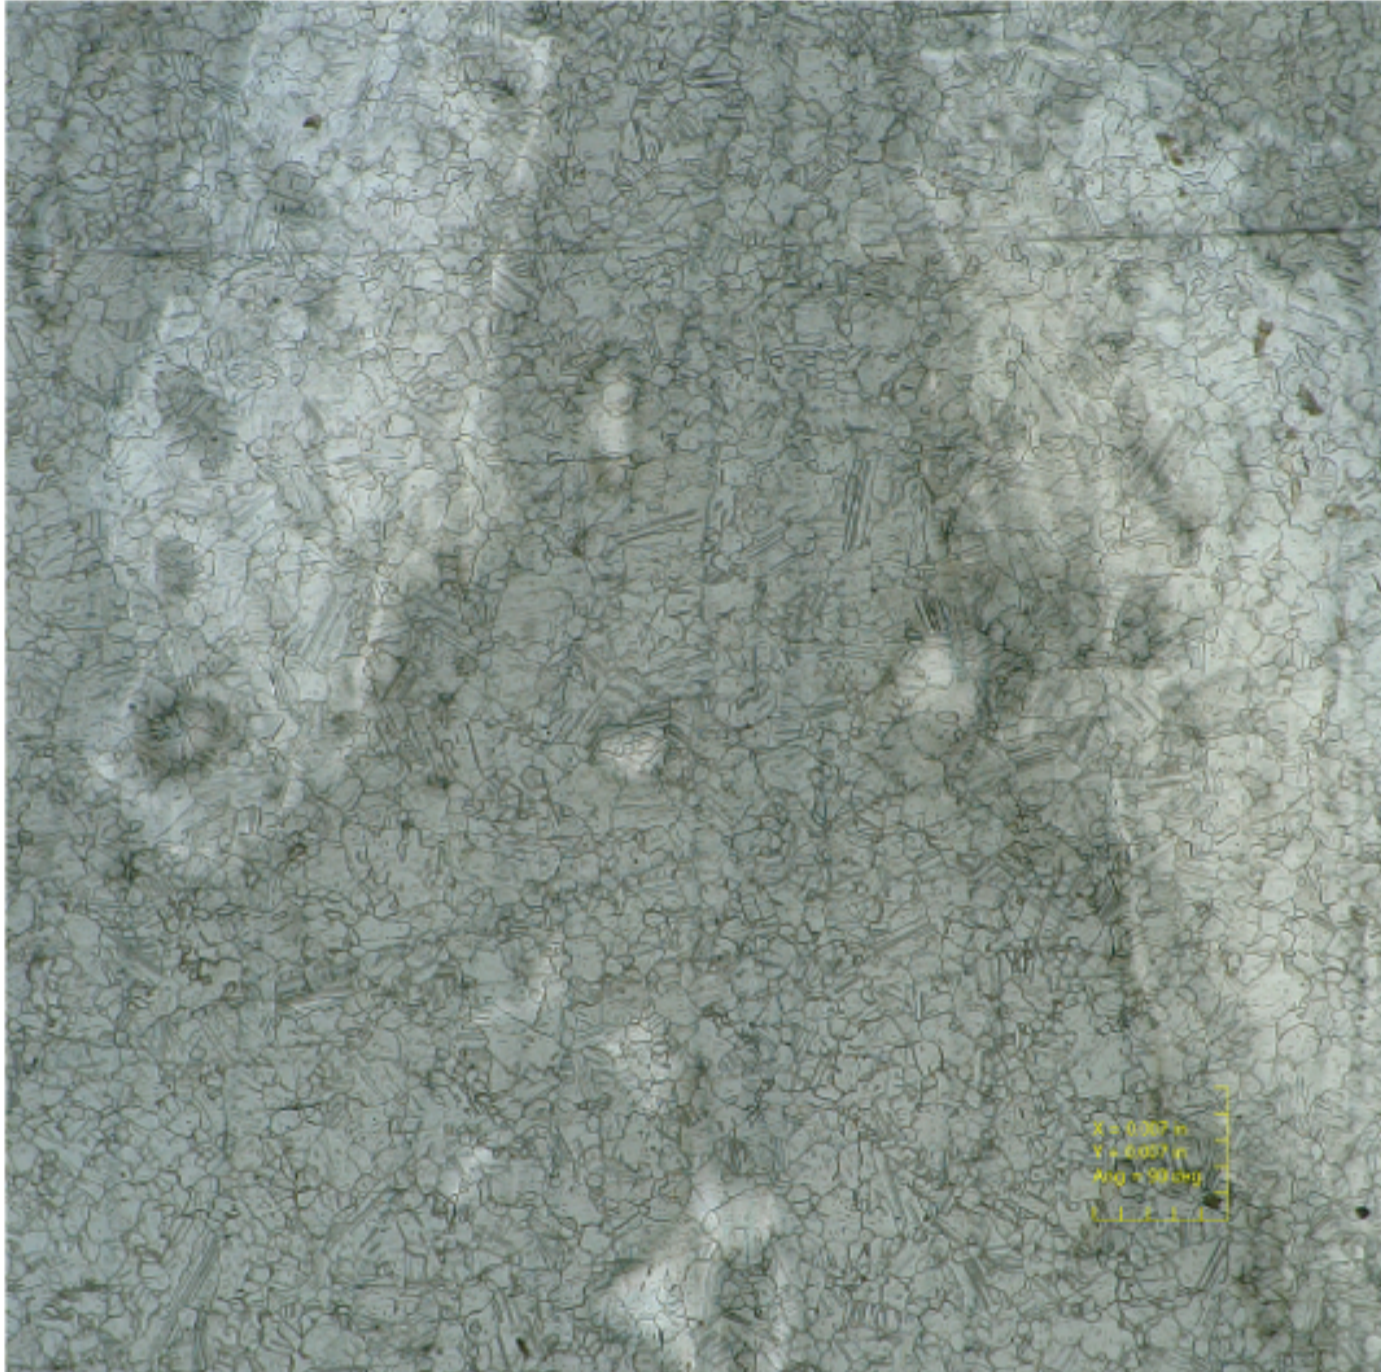


**BUBBLE REPLICA DEFECT  
RENE 88DT  
100X**

6038599-00

Figure 2 (Sheet 5) Replica with Region of Replica Tape that is Inadequately Adhered,  
that Produces a Bubbled Area

\* \* \* FOR ALL



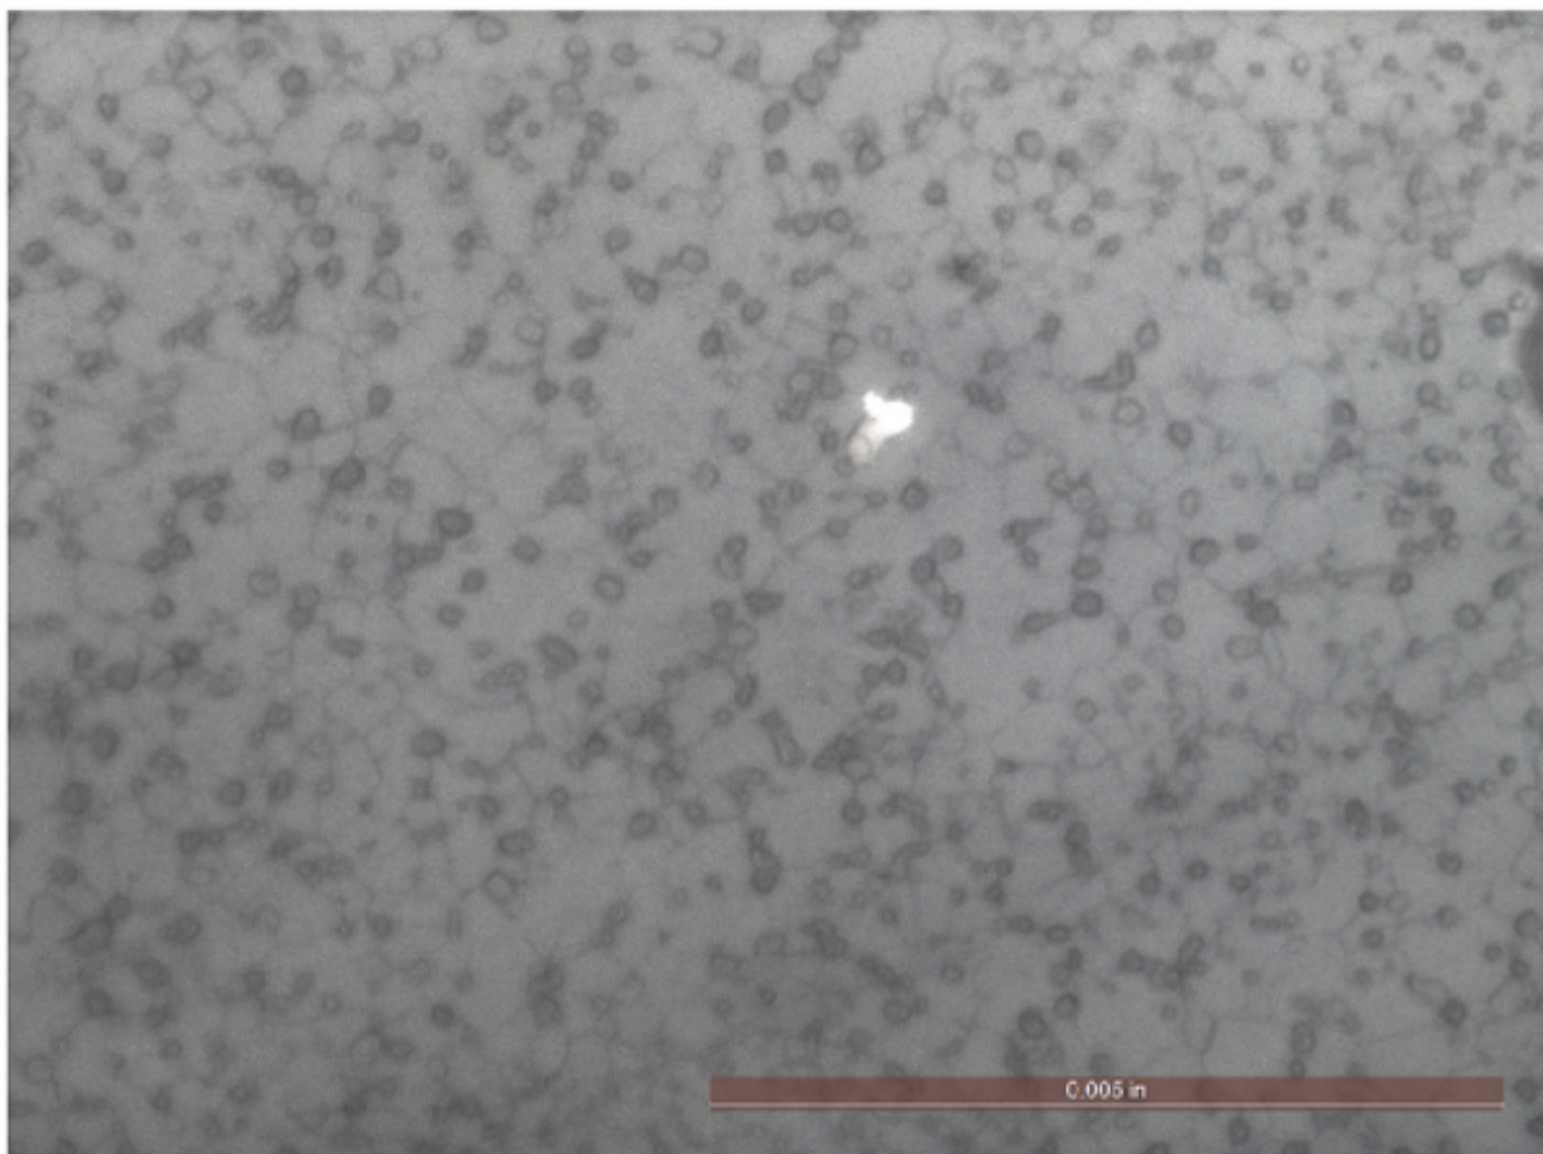

**BRIGHT SPOT REPLICA DEFECT FROM DEBRIS  
RENE 65  
500X**

6038600-00

Figure 2 (Sheet 6) Replica with Bright Spot due to Debris on the Surface Underneath the Replica Tape

GE Designated: - CONFIDENTIAL Subject to the restrictions on the media